

Bayesian optimal design accelerates discovery of material properties from bubble dynamics

Tianyi Chu^{1,*}, Jonathan B. Estrada², Spencer H. Bryngelson^{1,3}

¹School of Computational Science & Engineering, Georgia Institute of Technology, Atlanta, GA 30332, USA

²Department of Mechanical Engineering, University of Michigan, Ann Arbor, MI 48105, USA

³Daniel Guggenheim School of Aerospace Engineering, Georgia Institute of Technology, Atlanta, GA 30332, USA

Abstract

An optimal sequential experimental design approach is developed to characterize soft material properties at the high strain rates associated with bubble cavitation. The approach involves optimal design and model inference. The optimal design strategy maximizes the expected information gain in a Bayesian statistical setting to design experiments that provide the most informative cavitation data about unknown material properties. We infer constitutive models by characterizing the associated viscoelastic properties from measurements via a hybrid ensemble-based 4D-Var method (En4D-Var). The inertial microcavitation-based high strain-rate rheometry (IMR) method (Estrada et al. [1]) is used to simulate the bubble dynamics under laser-induced cavitation. Two sets of constitutive models demonstrate the method. We generate synthetic experimental data representing the viscoelastic behavior of stiff and soft polyacrylamide hydrogels. Accurate and efficient characterizations of the underlying models are presented.

1 Introduction

Large and rapid deformations in various materials, often caused by mechanical forces such as shock waves or lasers, can lead to failure in compliant fluid-containing materials like hydrogels and tissues. In particular, cavitation may occur when these materials are exposed to tensile waves, leading to high strain rates (10^3 – 10^8 1/s). Energy-focused cavitation, when used appropriately, can benefit various biological, medical, and surgical applications, including tissue phantom studies, laser surgery, and DNA manipulation in target cells [2–6]. However, accurate characterization of realistic soft materials and biotissues under such high strain rates and large deformations is challenging due to their common high compliance [7, 8], and mechanical behaviour beyond the linear elastic regime [9, 10]. Therefore, a sophisticated understanding of the constitutive response of the underlying tissue becomes substantial for accurately predicting the mechanical behavior at high strain rates.

Inertial microcavitation-based high strain-rate rheometry (IMR) has been proposed by Estrada et al. [1] for characterizing highly compliant materials at finite deformations and fast speeds. This high-strain rate rheometer combines laser-induced cavitation with physical bubble dynamics models to estimate the viscoelastic properties of hydrogels through observations of the bubble radius time history. The IMR method has been applied to characterize the mechanical behavior of several commonly used biomimetic hydrogels, including polyacrylamide (PA) [1, 11, 12], agarose [13, 14], and gelatin [15]. The time efficiency of the cavitation experiments, however, is limited by factors such as the chemical, degassing, and swelling protocols necessary to create pristine samples for

*Corresponding author

Email: tchu72@gatech.edu (Tianyi Chu)

Code available at https://github.com/InertialMicrocavitationRheometry/IMR_Bayesian_design

characterization [1, 16]. Therefore, an experimental design strategy is necessary to efficiently probe material responses to various physical mechanisms, such as deformation, pressure, and thermal effects, while preserving experimental or computational resources. This design approach is intended to be robust for characterizing various soft materials under different sources of uncertainty, including variations in experimental configuration and observational noise. We use the computationally efficient IMR method to develop a simulation-based optimal experimental design (OED) approach for material parameter characterizations and the physical models and theory that underpin them.

The IMR-based OED seeks to optimize the design of cavitation experiments to yield the most informative data about the viscoelastic properties of the unknown material. Following the decision-theoretic approach by Lindley [17], the relative entropy, or Kullback–Leibler (KL) divergence, from the posterior to the prior within the Bayesian statistical setting is often used to measure the information provided by an experiment. Therefore, the design process focuses on optimizing the expectation of this utility function, also known as the expected information gain (EIG). However, the direct calculation of the EIG is hindered by the intractability of the inherent double-loop integral due to the absence of closed forms and the inability of conventional Monte Carlo (MC) methods. Nonlinear models complicate the analytical integration of likelihood functions or posterior distributions, necessitating computational methods. Various approaches have been proposed to numerically evaluate the EIG, including nested Laplace approximations [18–21] and nested Monte-Carlo (NMC) estimators [22–25]. The Laplace approach systematically introduces bias, though NMC provides accurate estimators using a finite number of Monte Carlo samples.

Variational methods have also been incorporated into the EIG estimators to improve the convergence rate and accuracy [26, 27]. Readers are referred to Ryan et al. [28] and Rainforth et al. [29] for comprehensive reviews. With appropriate EIG estimators, the remaining task of Bayesian OED (BOED) is to optimize the EIG within the domain of design variables. Various optimization methods have been considered, such as simulated annealing [30], interacting particle systems [31], stochastic optimization [24, 32–34], and Bayesian optimization (BO) [26, 35, 36]. In this work, BO is the optimizer selected for its data efficiency, robustness to multi-modality, and ability to deal with noisy observations. We refer the reader to Shahriari et al. [37] and Snoek et al. [38] for a comprehensive review and practical implementation of BO, respectively. Instead of using the same design throughout the experimental process, sequential or adaptive designs have gained popularity in Bayesian design literature due to their flexibility and efficiency [25, 39–41]. In contrast to fixed experimental configurations in static designs, sequential designs aim to maximize the expected utility at each stage of experimentation based on the outcomes of previous experiments and the possible predictions of future ones. For cavitation rheometry, inferring material parameters from bubble dynamics data is important for proceeding with the sequential design.

We use data assimilation (DA) techniques for bubble-dynamics-based rheometry to improve predictions in uncertainty-prone high-strain-rate regimes. We combine the IMR method with observational data such as bubble-radius trajectories. The information needed to describe complex systems comes from different sources and has various characteristics, such as modeling assumptions and measurement noise. Each source is unlikely to fully observe the system, leading to information discrepancies between the theoretical model and the data. DA rectifies this problem by addressing uncertainty in the model and the data. In particular, the ensemble Kalman filter (EnKF) is an often-used DA tool due to its simple conceptual formulation and relative ease of implementation [42]. It achieves relatively high accuracy for a small ensemble, approximating the state as a multivariate Gaussian. Applications of EnKF include oceanography [43, 44], atmospheric science [45–47], and engineering [48]. Other variants of EnKF, such as ensemble Kalman smoother (EnKS) [49], iterative

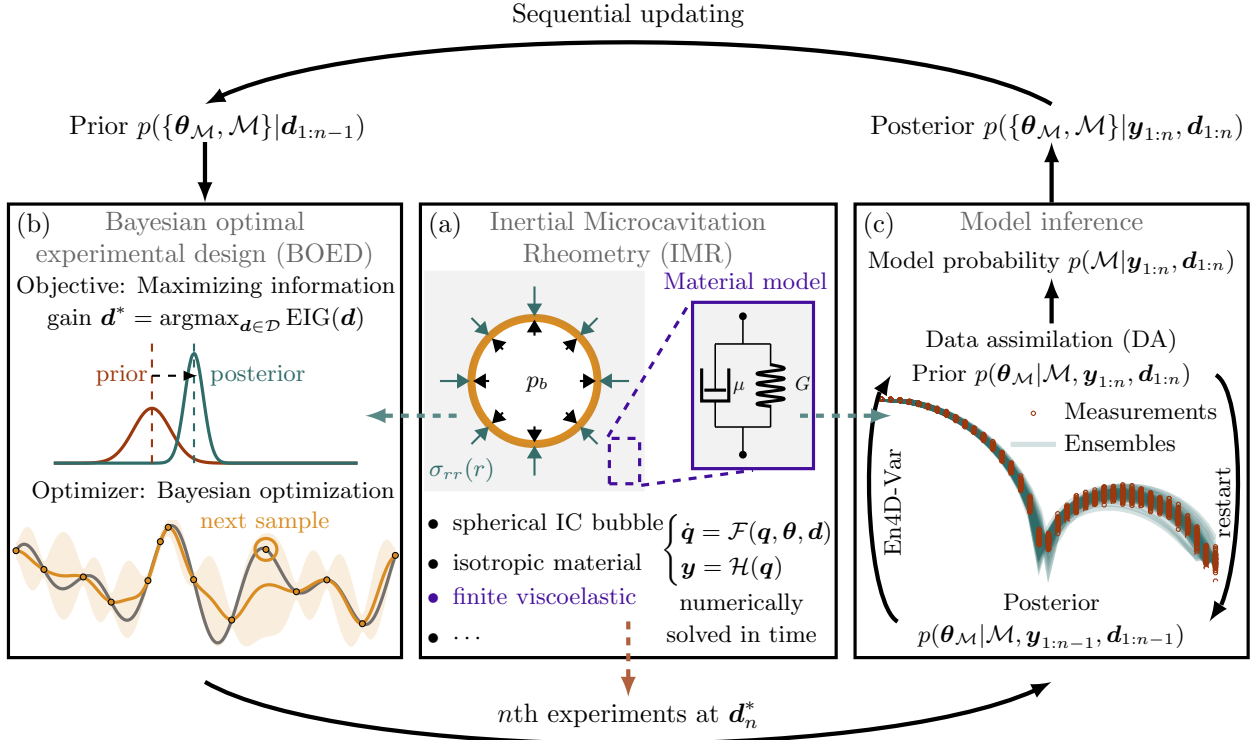


Figure 1: Schematic of the IMR-based sequential BOED. Given a modeling parameter, $\theta = \{\mathcal{M}, \theta_{\mathcal{M}}\}$, which includes a constitutive model and its material properties, and a design \mathbf{d} that describes the experimental setup (e.g., the equilibrium radius), the IMR approach numerically solved the spherically symmetric motion of bubble dynamics. In computation, the complete flow states \mathbf{q} include bubble radius, bubble-wall velocity, temperature, and other variables, but they are only partially observable and are denoted as \mathbf{y} .

EnKS [50, 51] and ensemble-based four-dimensional variational method (En4D-Var) [52, 53] have been explored. We refer the reader to Carrassi et al. [54] for a review of common DA methods.

Spratt et al. [55] incorporated several ensemble-based DA methods with the IMR solver to provide a scalable bubble-collapse rheometry framework. It reduces the number of simulations required for accurate characterizations from a large volume in the brute-force curve fitting strategy in Estrada et al. [1] to 48 ensembles, thereby offering significant computational advantages. The hybrid En4D-Var method also requires fewer measurements per data set to characterize the mechanical properties of hydrogels [13, 55]. DA methods require appropriate theoretical models as a *prior*, yet they do not provide information about how to select them. The most direct approach is to choose the model that minimizes the least-squares error. However, this approach does not consider the uncertainty from various sources, such as experimental setups or measurement errors. To address this, we use the Bayesian model selection framework [56, 57] to systematically determine the model probability in the presence of these uncertainties. We consider a library of potential constitutive models and calculate the likelihood of each model using the associated posterior distributions. The model parameters and probabilities are used to establish the sample space and determine the optimal EIG for optimal design. This approach systematically and sequentially infers the model from measurements via different experimental designs.

Figure 1 shows a graphical overview of the sequential BOED procedure we use herein. In section 2,

we introduce the IMR method and use it to conduct efficient bubble cavitation simulations. The optimal design process in [section 3](#) maximizes the EIG using BO to design the most informative cavitation experiments. The model inference part in [section 4](#) characterizes the unknown material properties, $\theta_{\mathcal{M}}$, of each constitutive model, \mathcal{M} , by analyzing the bubble dynamics trajectories, \mathbf{y} , using En4D-Var. Subsequently, it uses the marginal likelihood to calibrate the model probability. When the prior is updated using the posterior, one iteration of the sequential design is completed. Soft material properties are shown to be accurately and efficiently characterized by iterating optimal design and model inference processes. The performance of the sequential approach is demonstrated in [section 5](#) using two synthetic data sets for stiff and soft PA hydrogels. [Sections 6](#) and [7](#) summarize the main contributions and limitations.

2 Methods

2.1 Theoretical bubble dynamics model

Various spherical bubble dynamics models have been explored in the pursuit of characterizing the viscoelastic properties of surrounding materials; cavitation in soft materials is one prominent example [[1](#), [58–61](#)]. In these models, the Keller–Miksis equation [[62](#)] is applied to govern the spherically symmetric motion of bubble dynamics in a viscoelastic material assumed to be nearly incompressible. Upon nondimensionalization using the maximum bubble radius, R_{\max} , the far-field pressure, p_{∞} , the surrounding material density ρ , and the far-field temperature T_{∞} , the dimensionless Keller–Miksis equation is

$$\left(1 - \frac{\dot{R}^*}{c^*}\right) R^* \ddot{R}^* + \frac{3}{2} \left(1 - \frac{\dot{R}^*}{3c^*}\right) \dot{R}^{*2} = \left(1 + \frac{\dot{R}^*}{c^*} + \frac{R^*}{c^*} \frac{d}{dt}\right) \left(p_b^* - \frac{1}{\text{We} \dot{R}^*} + S^* - 1\right). \quad (1)$$

The details of dimensionless parameters are summarized in [table 1](#). The bubble contents are assumed to consist of two components: water vapor and gas considered to be non-condensable on the time scales of inertial cavitation [[63](#), [64](#)]. This mixture is assumed to be homobaric and follow the ideal gas law and the time-dependent pressure inside the bubble, $p_b^*(t)$, is coupled to the energy equation [[1](#), [61](#)]. We assume that the mass and heat transfer of the gases within the bubble obeys Fick’s law and Fourier’s law. By neglecting the initial bubble growth phase, the laser-induced cavitation model begins when the bubble reaches its maximum radius and thermodynamic equilibrium, $R^*(0) = 1$.

While the Keller–Miksis equation accurately describes spherical bubble dynamics to first order in the Mach number, appropriate constitutive relations are necessary to model the dynamic behavior of the surrounding media in terms of the time-dependent stress integral, $S^*(t)$. Combinations of springs and dashpots, such as the Kelvin–Voigt and Maxwell models, are often used to account for the significant change in strain rate throughout the bubble expansion-collapse life cycles during an inertial microcavitation event. We aim to develop a systematic method for selecting appropriate viscoelastic constitutive models for various gel specimens. To this end, we examine a range of constitutive models for the surrounding media, as described in [table 2](#). Specifically, the Kelvin–Voigt model, incorporating either just a Neo-Hookean elastic term [[58](#)] or an additional second-order strain-stiffening term [[11](#)], often better represents the nonlinear viscoelastic behavior at high strain rates [[14](#)]. These two models are different orders of Taylor expansion of the more general Fung model [[65](#)]. More models are available, but they are beyond the scope of this work. The stress

Table 1: Dimensionless quantities.

Dimensional	Dimensionless quantity	Quantity name
	$U_c = \sqrt{p_\infty/\rho}$	Characteristic velocity
	$\lambda = R/R_\infty$	Material stretch ratio
t	$t^* = tU_c/R_{\max}$	Time
R	$R^* = R/R_{\max}$	Bubble-wall radius
U	$U^* = U/U_c$	Bubble-wall velocity
R_∞	$R_\infty^* = R_\infty/R_{\max}$	Equilibrium bubble-wall radius
c	$c^* = c/U_c$	Material wave speed
p_b	$p_b^* = p_b/p_\infty$	Bubble-wall pressure
R_{\max}	$We = p_\infty R_{\max}/(2\gamma)$	Weber number
S	$S^* = S/p_\infty$	Stress integral
G	$1/Ca = G/p_\infty$	1/Cauchy number
μ	$1/Re = \mu/(\rho U_c R_{\max})$	1/Reynolds number

integral associated with the quadratic law Kelvin–Voigt (qKV) model is

$$S^* = \overbrace{-\frac{4U^*}{ReR^*} - \frac{1}{2Ca_\infty} \left[5 - \frac{4}{\lambda} - \frac{1}{\lambda^4} \right]}^{\text{Neo-Hookean Kelvin-Voigt}} + \frac{\alpha}{Ca_\infty} \left[\frac{177}{20} + \frac{1}{4\lambda^8} + \frac{2}{5\lambda^5} - \frac{3}{2\lambda^4} + \frac{2}{\lambda^2} - \frac{6}{\lambda} - 4\lambda \right], \quad (2)$$

where α represents strain stiffening when positive and strain softening when negative [66]. A lower bound of α to maintain positive strain energy is $\alpha \geq -2/(2\lambda^2 + 1/\lambda^4 - 3)$. When $\alpha = 0$, (2) reduces to the same form of the stress integral for the Neo-Hookean model, in which dynamic shear moduli are used instead of the quasistatic moduli to account for the strain stiffening effect during cavitation. For more details, readers are referred to Estrada et al. [1]. Recently, Mancina et al. [13] proposed a generalized variant of qKV (Gen. qKV) that extends the capability to accommodate variations in the ground-state shear modulus, G_∞ , traditionally considered constant in the qKV model. Later, we will adopt this Gen. qKV model to account for the measurement error in the quasistatic shear modulus.

Table 2: Summary of constitutive models under consideration.

Model \mathcal{M}	Description	Material properties $\theta_{\mathcal{M}}$
	Newtonian Fluid	1/Re
NHE [67]	Neo-Hookean Elastic	1/Ca
NHKV [58]	Neo-Hookean Kelvin–Voigt	1/Re, 1/Ca
qKV [11]	Quadratic Law Kelvin–Voigt	1/Re, α , 1/Ca $_\infty$
Gen. qKV [68]	Generalized qKV	1/Re, α , 1/Ca $_\infty$

We use the modeling parameter

$$\theta \equiv \{\mathcal{M}, \theta_{\mathcal{M}}\} \quad (3)$$

to represent a candidate mathematical constitutive model and its material properties. The design

parameter is

$$\mathbf{d} \equiv \{\text{We}, R_\infty^*\}, \quad (4)$$

representing the experimental free parameters. Following Estrada et al. [1], in the physical context of interest, we regard densities, pressures, and temperatures as constants, though this is not a restriction of the method. We use IMR to simulate forward-time bubble dynamics with known error signatures, which we represent as Gaussian noise in the model error and measurement noise.

2.2 Numerical methods

The state vector is

$$\mathbf{q}(t) = \{R^*, \dot{R}^*, p_b, S^*, T^*, C^*, 1/\text{Ca}, 1/\text{Re}, \alpha\}, \quad (5)$$

where the state parameters represent the bubble-wall radius, velocity, bubble pressure, stress integral, the discretized temperature and vapor concentration fields inside the bubble, the reciprocal-Cauchy and reciprocal-Reynolds numbers, and the strain-stiffening parameter, respectively. The discrete-time nonlinear dynamical system takes the form of

$$\mathbf{q}_{k+1} = \mathcal{F}_k(\mathbf{q}_k, \mathbf{d}), \quad (6a)$$

$$R_{k+1}^* = \mathcal{H}(\mathbf{q}_{k+1}), \quad (6b)$$

where \mathcal{F}_k is the nonlinear operator given the time steps, and \mathcal{H} is the linear observation function that maps the state \mathbf{q} to measurement space. In this study, we designate the bubble radius R^* as the primary observable variable due to its direct measurability in experimental setups. For a given time interval $t \in [0, T]$ with N_t time steps, the deterministic model outputs, $\tilde{\mathbf{Q}} = [\mathbf{q}_1 \ \cdots \ \mathbf{q}_{N_t}]$, and the corresponding bubble dynamics measurements, $\tilde{\mathbf{Y}} = [R^* \ \cdots \ R_{N_t}^*]$, can be collected as

$$\tilde{\mathbf{Q}} = \mathcal{F}(\boldsymbol{\theta}, \mathbf{d}) \quad \text{and} \quad \tilde{\mathbf{Y}} = \mathcal{H}(\tilde{\mathbf{Q}}), \quad (7a)$$

where \mathcal{F} represents the nonlinear operator that generates the space-time states at all time instances.

Following a procedure similar to Freund and Ewoldt [69], we incorporate the deterministic IMR solver in (7a) with the model error $\boldsymbol{\epsilon}_m$ and the experimental error $\boldsymbol{\epsilon}_e$ to approximate experimental measurements, such that

$$\mathbf{Q}_m = \tilde{\mathbf{Q}} + \boldsymbol{\epsilon}_m = \mathcal{F}(\boldsymbol{\theta}, \mathbf{d}) + \boldsymbol{\epsilon}_m, \quad \text{where} \quad \boldsymbol{\epsilon}_m \sim \mathcal{N}(\mathbf{0}, \boldsymbol{\Sigma}_m), \quad \text{and} \quad (8a)$$

$$\mathbf{Y} = \mathbf{Y}_m + \boldsymbol{\epsilon}_e = \mathcal{H}(\mathbf{Q}_m) + \boldsymbol{\epsilon}_e, \quad \text{where} \quad \boldsymbol{\epsilon}_e \sim \mathcal{N}(\mathbf{0}, \boldsymbol{\Sigma}_e). \quad (8b)$$

The observation function \mathcal{H} is linear, so (7) can be written as

$$\mathbf{Y} = \tilde{\mathbf{Y}} + \boldsymbol{\epsilon} = \mathcal{H} \circ \mathcal{F}(\boldsymbol{\theta}, \mathbf{d}) + \boldsymbol{\epsilon}, \quad \text{where} \quad \boldsymbol{\epsilon} \sim \mathcal{N}(\mathbf{0}, \boldsymbol{\Sigma}), \quad (8)$$

where $\boldsymbol{\epsilon}$ is the combined error from the model and the experiments, and the true bubble dynamics, $\tilde{\mathbf{Y}}$, are unobtainable from the measurements. In the following, (8) generates synthetic measurements.

3 Simulation-based Bayesian optimal experimental design

The goal of the optimal design procedure is to find a design point, \mathbf{d}^* , that maximizes the expectation of a utility function, $u(\mathbf{d}, \mathbf{Y}, \boldsymbol{\theta})$. That is,

$$\mathbf{d}^* = \operatorname{argmax}_{\mathbf{d} \in \mathcal{D}} \mathbb{E}\{u(\mathbf{d}, \mathbf{Y}, \boldsymbol{\theta})\} = \operatorname{argmax}_{\mathbf{d} \in \mathcal{D}} \int_{\mathcal{Y}} \int_{\Theta} u(\mathbf{d}, \mathbf{Y}, \boldsymbol{\theta}) p(\boldsymbol{\theta} | \mathbf{d}, \mathbf{Y}) p(\mathbf{Y} | \mathbf{d}) \, d\boldsymbol{\theta} \, d\mathbf{Y}. \quad (9)$$

The inference of parameters $\boldsymbol{\theta}$ can be obtained based on the prior distribution observations and Bayes' rule,

$$\underbrace{p(\boldsymbol{\theta} | \mathbf{Y}, \mathbf{d})}_{\text{Posterior}} = \frac{\overbrace{p(\mathbf{Y} | \boldsymbol{\theta}, \mathbf{d})}^{\text{Likelihood}} \overbrace{p(\boldsymbol{\theta} | \mathbf{d})}^{\text{Prior}}}{\underbrace{p(\mathbf{Y} | \mathbf{d})}_{\text{Evidence}}}. \quad (10)$$

The probability $p(\boldsymbol{\theta})$ can be separated as

$$p(\boldsymbol{\theta}) = p(\mathcal{M}) p(\boldsymbol{\theta}_{\mathcal{M}} | \mathcal{M}), \quad (11)$$

which contains the probability of the mathematical constitutive model \mathcal{M} and the probability of the corresponding material parameters. From (8), the likelihood function is

$$p(\mathbf{Y} | \boldsymbol{\theta}, \mathbf{d}) = \frac{1}{\sqrt{(2\pi)^{N_t} |\boldsymbol{\Sigma}|}} \exp \left[-\frac{1}{2} (\mathbf{Y} - \mathcal{H} \circ \mathcal{F}(\boldsymbol{\theta}, \mathbf{d})) \boldsymbol{\Sigma}^{-1} (\mathbf{Y} - \mathcal{H} \circ \mathcal{F}(\boldsymbol{\theta}, \mathbf{d}))^\top \right], \quad (12)$$

and the evidence is obtained through integration as

$$p(\mathbf{Y} | \mathbf{d}) = \int_{\Theta} p(\mathbf{Y} | \boldsymbol{\theta}, \mathbf{d}) p(\boldsymbol{\theta}) \, d\boldsymbol{\theta}. \quad (13)$$

The maximum information gain from the prospective experiment follows from using a relative entropy utility function, which is the same as the Kullback–Leibler (KL) divergence between the posterior and prior [17], so

$$u(\mathbf{d}, \mathbf{Y}, \boldsymbol{\theta}) = D_{\text{KL}}(\text{posterior} \parallel \text{prior}) = \int_{\Theta} p(\boldsymbol{\theta} | \mathbf{d}, \mathbf{Y}) \log \left[\frac{p(\boldsymbol{\theta} | \mathbf{d}, \mathbf{Y})}{p(\boldsymbol{\theta})} \right] \, d\boldsymbol{\theta} = u(\mathbf{d}, \mathbf{Y}). \quad (14)$$

This choice of utility function is not a function of the parameters $\boldsymbol{\theta}$. The expectation of the KL divergence is then

$$\mathbb{E}\{u(\mathbf{d}, \mathbf{Y}, \boldsymbol{\theta})\} = \int_{\mathcal{Y}} \int_{\Theta} p(\boldsymbol{\theta} | \mathbf{d}, \mathbf{Y}) \log \left[\frac{p(\boldsymbol{\theta} | \mathbf{d}, \mathbf{Y})}{p(\boldsymbol{\theta})} \right] \, d\boldsymbol{\theta} p(\mathbf{Y} | \mathbf{d}) \, d\mathbf{Y} \quad (15)$$

$$= \int_{\mathcal{Y}} \int_{\Theta} \log \left[\frac{p(\mathbf{Y} | \boldsymbol{\theta}, \mathbf{d})}{p(\mathbf{Y} | \mathbf{d})} \right] p(\mathbf{Y} | \boldsymbol{\theta}, \mathbf{d}) p(\boldsymbol{\theta}) \, d\boldsymbol{\theta} \, d\mathbf{Y}, \quad (16)$$

where the Bayes' rule in (10) is applied. This quantity is also known as the expected information gain (EIG). Further, $p(\boldsymbol{\theta} | \mathbf{d}) = p(\boldsymbol{\theta})$, as specifying \mathbf{d} does not provide further information regarding $\boldsymbol{\theta}$. In practice, the double integral in (15) cannot be computed analytically and is expensive to approximate. To address this, a double-loop Monte Carlo (DLMC) estimator, also known as the

nested MC (NMC) estimator, approximates the EIG [23]. It is

$$\text{EIG}(\mathbf{d}) \approx \mu_{\text{NMC}}(\mathbf{d}) \equiv \sum_{j=1}^{N_2} \log \left[\frac{p(\mathbf{Y}^{(j)} | \boldsymbol{\theta}^{(0,j)}, \mathbf{d})}{\frac{1}{N_1} \sum_{i=1}^{N_1} p(\mathbf{Y}^{(j)} | \boldsymbol{\theta}^{(i,j)}, \mathbf{d})} \right], \quad (17)$$

where $\boldsymbol{\theta}^{(i,j)} \stackrel{\text{i.i.d.}}{\sim} p(\boldsymbol{\theta})$ and $\mathbf{Y}^{(j)} \stackrel{\text{i.i.d.}}{\sim} p(\mathbf{Y} | \boldsymbol{\theta}^{(0,j)}, \mathbf{d})$. To obtain the dependent pair $(\boldsymbol{\theta}^{(i,j)}, \mathbf{q}^{(i)})$, the importance sampling technique is used: we first draw $\boldsymbol{\theta}^{(i,j)}$ from the prior $p(\boldsymbol{\theta})$, and then draw $\mathbf{Y}^{(i)}$ from the conditional distribution $p(\mathbf{Y} | \boldsymbol{\theta}^{(i,j)}, \mathbf{d})$. In the computation, the samples $\boldsymbol{\theta}^{(i,j)}$ are collected using the sample reused technique [24]. This technique uses a batch of prior samples $\{\boldsymbol{\theta}^{(l)}\}_{l=1}^{N_2}$ for both the inner and outer Monte Carlo sums, therefore reducing the computational cost from $O(N_1 N_2)$ to $O(N_2)$. In the following, we use the notation N_{EIG} to represent the sample size used for approximating the EIG.

In practical settings, experiments and data collection for inertial cavitation are carried out separately due to the need to prepare hydrogel specimens for different experimental setups. Thus, a sequential experimental design is important for this purpose. We assume that the experiment outcomes are conditionally independent, given the latent variables and designs,

$$p(\mathbf{Y}_{1:N_{\text{Des}}}, \boldsymbol{\theta} | \mathbf{d}_{1:N_{\text{Des}}}) = p(\boldsymbol{\theta}) \prod_{n=1}^{N_{\text{Des}}} p(\mathbf{Y}_n | \boldsymbol{\theta}, \mathbf{d}_n). \quad (18)$$

Having conducted experiments $1, 2, \dots, N_{\text{Des}} - 1$, the design $\mathbf{d}_{N_{\text{Des}}}$ for the prospective experiment can be obtained by replacing the prior, $p(\boldsymbol{\theta})$, with $p(\boldsymbol{\theta} | \mathbf{d}_{1:N_{\text{Des}}-1}, \mathbf{Y}_{1:N_{\text{Des}}-1})$ in (10) such that

$$p(\boldsymbol{\theta} | \mathbf{Y}_{1:N_{\text{Des}}}, \mathbf{d}_{1:N_{\text{Des}}}) = \frac{p(\mathbf{Y}_{N_{\text{Des}}} | \boldsymbol{\theta}, \mathbf{d}_{N_{\text{Des}}}) p(\boldsymbol{\theta} | \mathbf{Y}_{1:N_{\text{Des}}-1}, \mathbf{d}_{1:N_{\text{Des}}-1})}{p(\mathbf{Y}_{N_{\text{Des}}} | \mathbf{d}_{N_{\text{Des}}})} = \dots = \frac{p(\boldsymbol{\theta}) \prod_{n=1}^{N_{\text{Des}}} p(\mathbf{Y}_n | \boldsymbol{\theta}, \mathbf{d}_n)}{p(\mathbf{Y}_{1:N_{\text{Des}}} | \mathbf{d}_{1:N_{\text{Des}}})}. \quad (19)$$

Similar to (15), the EIG for N_{Des} is approximated in a Markovian fashion as

$$\text{EIG}(\mathbf{d}_{N_{\text{Des}}}) \approx \sum_{j=1}^{N_{\text{EIG}}} \log \left[\frac{p(\mathbf{Y}_{N_{\text{Des}}}^{(j)} | \boldsymbol{\theta}_{N_{\text{Des}}}^{(0,j)}, \mathbf{d}_{N_{\text{Des}}})}{\frac{1}{N_{\text{EIG}}} \sum_{i=1}^{N_{\text{EIG}}} p(\mathbf{Y}_{N_{\text{Des}}}^{(j)} | \boldsymbol{\theta}_{N_{\text{Des}}}^{(i,j)}, \mathbf{d}_{N_{\text{Des}}})} \right], \quad (20)$$

where $\boldsymbol{\theta}_{N_{\text{Des}}}^{(i,j)} \stackrel{\text{i.i.d.}}{\sim} p(\boldsymbol{\theta} | \mathbf{Y}_{1:N_{\text{Des}}-1}, \mathbf{d}_{1:N_{\text{Des}}-1})$ and $\mathbf{Y}_{N_{\text{Des}}}^{(j)} \stackrel{\text{i.i.d.}}{\sim} p(\mathbf{Y} | \boldsymbol{\theta}_{N_{\text{Des}}}^{(0,j)}, \mathbf{d}_{N_{\text{Des}}})$. Through this, we conduct an adaptive sequential experiment that iteratively optimizes the selection of the design $\mathbf{d}_{N_{\text{Des}}}$ at each step. This leads to the sequential optimization problem

$$\mathbf{d}_{N_{\text{Des}}}^* = \underset{\mathbf{d}_{N_{\text{Des}}} \in \mathcal{D}}{\text{argmax}} \text{EIG}(\mathbf{d}_{N_{\text{Des}}}), \quad (21)$$

Given an EIG estimator, various methods can be used for (21), including some specifically developed for BOED [24, 30, 31]. In this work, Bayesian optimization (BO) is selected for the subsequent design optimization, given its advantageous features such as sample efficiency, robustness to multi-modality, and inherent capability to handle noisy objective evaluations [70]. Following Snoek et al. [38], we use the Ard Matérn 5/2 kernel for Gaussian process (GP) regression and the expected improvement criterion for the acquisition function. In practice, BO is initialized with N_{INT} random samples to create a more reasonable initial GP model [71–73]. A total number of N_{BO} BO trials is used to obtain the optimal design.

Algorithm 1 Bayesian optimal experimental design (refer to [fig. 1](#) (b) for graphical illustration)

Input: prior $p(\boldsymbol{\theta}|\mathbf{d}_{1:N_{\text{Des}}})$, error variance $\boldsymbol{\Sigma}$, EIG sample size N_{EIG}
Output: Next design point $\mathbf{d}_{N_{\text{Des}}+1}^*$

- 1: Evaluate EIG for the N_{INT} random points
- 2: **for** $l = N_{\text{INT}} + 1 : N_{\text{BO}}$ **do**
- 3: Perform Gaussian process regression based on the evaluated values, $\{\text{EIG}(\mathbf{d}_{N_{\text{Des}}+1}^{(l')})\}_{l'=1}^l$
- 4: Obtain next search point, $\mathbf{d}_{N_{\text{Des}}+1}^{(l+1)}$, that maximizes expected improvement
- 5: Evaluate $\text{EIG}(\mathbf{d}_{N_{\text{Des}}+1}^{(l+1)})$
- 6: **end for**
- 7: Obtain the optimal design point $\mathbf{d}_{N_{\text{Des}}+1}^*$ that maximizes the EIG
- 1: **function** $\text{EIG}(\mathbf{d}; p(\boldsymbol{\theta}|\mathbf{d}_{1:N_{\text{Des}}}); N_{\text{EIG}})$
- 2: Draw $N_{\text{EIG}} + 1$ samples $(\boldsymbol{\theta}^{(0)}, \boldsymbol{\theta}^{(1)}, \dots, \boldsymbol{\theta}^{(N_{\text{EIG}})})$ from prior $p(\boldsymbol{\theta}|\mathbf{d}_{1:N_{\text{Des}}})$
- 3: Draw N_{EIG} $R(t)$ samples $(\mathbf{Y}^{(1)}, \dots, \mathbf{Y}^{(N_{\text{EIG}})})$ from likelihood $p(\mathbf{Y}|\boldsymbol{\theta}^{(0)}, \mathbf{d})$ with Gaussian error $\boldsymbol{\Sigma}$
- 4: **for** $i = 1 : N_{\text{EIG}}$ **do**
- 5: Perform the IMR simulation for the design \mathbf{d} using the parameter $\boldsymbol{\theta}^{(i)}$
- 6: Evaluate the likelihood $p(\mathbf{Y}^{(j)}|\boldsymbol{\theta}^{(i)}, \mathbf{d})$ with Gaussian error $\boldsymbol{\Sigma}$
- 7: **end for**
- 8: Calculate the EIG using [\(15\)](#)
- 9: **end function**

An algorithm for IMR-based BOED is outlined in [algorithm 1](#). This offers a systematic approach to identifying the optimal design for the next experiment. The next step involves characterizing the material properties based on the measurements of bubble dynamics, as detailed below.

4 Model inference

4.1 Data assimilation

With data collected from experiments or simulations on inertial cavitation, the remaining task is to find the most accurate model for characterizing bubble dynamics within uncertainty-prone high-strain-rate regimes. Here, we adopt the En4D-Var approach due to its computational efficiency [\[13, 55\]](#). Under the assumption that the variables being considered follow a multivariate Gaussian distribution, the En4D-Var filter can be broken down into a forecast and an analysis step.

Given the initial N_{En} ensembles

$$\tilde{\mathbf{Q}}_0 = \begin{bmatrix} \tilde{\mathbf{Q}}_0^{(1)} & \dots & \tilde{\mathbf{Q}}_0^{(N_{\text{En}})} \end{bmatrix}, \quad (22)$$

the states can be propagated in time using [\(6\)](#) and the corresponding ensemble bubble radii at time step k can be represented as

$$\tilde{\mathbf{Y}}_k = \begin{bmatrix} R_k^{*(1)} & \dots & R_k^{*(N_{\text{En}})} \end{bmatrix}. \quad (23)$$

For a given observed data set, \mathbf{Y}^{D} , and a data assimilation window size, N_t , the cost function of

En4D-Var is

$$J(\mathbf{Q}_0) = \frac{1}{2N_t} \sum_{k=1}^{N_t} \|\mathbf{Y}_k^{\text{D}} - \mathbf{Y}_k(\mathbf{Q}_0)\|_{\mathbf{P}_k}^2 + \frac{1}{2} \|\mathbf{Q}_0 - \tilde{\mathbf{Q}}_0\|_{\mathbf{C}_0^{-1}}^2. \quad (24)$$

The norms for the input and output spaces are

$$\|\mathbf{Y}_k\|_{\mathbf{P}_k}^2 \equiv \mathbf{Y}_k^\top \mathbf{P}_k^{-1} \mathbf{Y}_k \quad \text{and} \quad \|\mathbf{Q}_0\|_{\mathbf{C}_0}^2 \equiv \mathbf{Q}_0^\top \mathbf{C}_0^{-1} \mathbf{Q}_0, \quad (25)$$

where \mathbf{P}_k is the measurement noise covariance matrix at time step k , and $\mathbf{C}_0 = \tilde{\mathbf{Q}}_0' \tilde{\mathbf{Q}}_0'^\top$ is the initial ensemble covariance defined using the initial state perturbation matrix,

$$\tilde{\mathbf{Q}}_0' = \frac{1}{\sqrt{N_{\text{En}} - 1}} \left[\tilde{\mathbf{Q}}_0^{(1)} - \langle \tilde{\mathbf{Q}}_0 \rangle \quad \cdots \quad \tilde{\mathbf{Q}}_0^{(N_{\text{En}})} - \langle \tilde{\mathbf{Q}}_0 \rangle \right], \quad (26)$$

where $\langle \cdot \rangle$ is the ensemble average. The optimization for the cost function in (24) is carried out using the form $\mathbf{Q}_0 = \tilde{\mathbf{Q}}_0 + \tilde{\mathbf{Q}}_0' \cdot \mathbf{w}$ to restrict the solution to the subspace spanned by the scaled perturbation matrix around the initial ensembles using the correction coefficient \mathbf{w} . This is equivalent to finding the minimizer

$$\mathbf{w}_{\text{opt}} = \underset{\mathbf{w}}{\text{argmin}} J_w(\mathbf{w}) \quad (27)$$

for the cost function

$$J_w(\mathbf{w}) = \frac{1}{2N_t} \sum_{k=1}^{N_t} \|\mathbf{Y}_k^{\text{D}} - \tilde{\mathbf{Y}}_k - \tilde{\mathbf{Y}}_k' \cdot \mathbf{w}\|_{\mathbf{P}_k}^2 + \frac{1}{2} \mathbf{w}^\top \mathbf{w}, \quad (28)$$

where the scaled output perturbation matrix takes the form of

$$\tilde{\mathbf{Y}}_k' = \frac{1}{\sqrt{N_{\text{En}} - 1}} \left[\tilde{\mathbf{Y}}_k^{(1)} - \langle \tilde{\mathbf{Y}}_k \rangle \quad \cdots \quad \tilde{\mathbf{Y}}_k^{(N_{\text{En}})} - \langle \tilde{\mathbf{Y}}_k \rangle \right]. \quad (29)$$

In practice, we follow Bocquet and Sakov [50] to seek the optimal correction coefficient \mathbf{w}_{opt} iteratively using a Gauss–Newton method,

$$\mathbf{w}_{i+1} = \mathbf{w}_i - \mathcal{H}_i^{-1} \Delta J_i(\mathbf{w}_i), \quad (30)$$

where $i < N_{\text{iter}}$ is the iteration index. The Hessian and gradient of J can be found with

$$\mathcal{H}_i = (N_{\text{En}} - 1) \mathbf{I} + \frac{1}{N_t} \sum_{k=1}^{N_t} \tilde{\mathbf{Y}}_k' \tilde{\mathbf{Y}}_k'^\top \mathbf{P}_k^{-1} \tilde{\mathbf{Y}}_k', \quad (31)$$

$$\Delta J_i = -\frac{1}{N_t} \sum_{k=1}^{N_t} \tilde{\mathbf{Y}}_k' \tilde{\mathbf{Y}}_k'^\top \mathbf{P}_k^{-1} (\mathbf{Y}_k^{\text{D}} - \tilde{\mathbf{Y}}_k) + (N_{\text{En}} - 1) \mathbf{w}_i. \quad (32)$$

Three enhancements are introduced here. First, the reciprocal-Cauchy and reciprocal-Reynolds numbers, $1/\text{Ca}$ and $1/\text{Re}$, are incorporated into the state vector in (5) to guarantee Gaussian distributions of the physical quantities, G and μ . Second, the parameter α can be negative,

corresponding to strain-softening, when the quasistatic shear modulus, G_∞ , is overestimated. Third, instead of performing En4D-Var for every measurement independently and then collecting all the posterior ensembles, we consider an iterative-restart strategy to reduce the computational cost and bias from the prior. A similar restart strategy has been used in the restart-EnKF to address the dynamical systems with strong nonlinearity [74–76]. We apply En4D-var to the data mean, and the measurement noise matrix \mathbf{P}_k at each time step is obtained from the data. After obtaining the posterior ensembles, we restart the data assimilation process by drawing fresh samples from the inflated posterior distribution. Here, the “Relaxation Prior to Spread” (RTPS) scheme addresses the sampling error in ensemble methods due to finite ensemble size [77]. The variances are updated as

$$\sigma_i = \sigma_i^{(\text{post})} + a \left(\sigma_i^{(\text{prior})} - \sigma_i^{(\text{post})} \right), \quad (33)$$

where $a = 0.7$ is an inflation parameter [55]. We repeat this process, and the final posterior distributions are obtained through N_{runs} complete cycles. The total number of runs required for the DA is therefore $N_{\text{DA}} = N_{\text{iter}} N_{\text{runs}}$.

4.2 Model probability

After performing data assimilation for available models, the next step is to choose models that best represent the experimental measurements. The most straightforward way is to select the model with the least-squares error. This strategy, however, does not account for the uncertainty in measurements. To tackle this, we calculate the probability of each model from the En4D-Var outputs using the Bayesian model selection framework [56, 57]. Given the measurement data \mathbf{Y}^{D} , the marginal likelihood of each model \mathcal{M} can be calculated as

$$p(\mathcal{M}|\mathbf{Y}^{\text{D}}, \mathbf{d}) = \frac{p(\mathcal{M})}{p(\mathbf{Y}^{\text{D}}|\mathbf{d})} \int_{\Theta} p(\mathbf{Y}^{\text{D}}|\mathcal{M}, \boldsymbol{\theta}_{\mathcal{M}}, \mathbf{d}) p(\boldsymbol{\theta}_{\mathcal{M}}|\mathcal{M}, \mathbf{d}) d\boldsymbol{\theta}_{\mathcal{M}}. \quad (34)$$

Similar to (17), importance sampling can be used to approximate the marginal likelihood as

$$p(\mathcal{M}|\mathbf{Y}^{\text{D}}, \mathbf{d}) \approx \frac{1}{N_{\text{En}}} \sum_{i=1}^{N_{\text{En}}} p(\mathbf{Y}^{\text{D}}|\mathcal{M}, \boldsymbol{\theta}_{\mathcal{M}}^{(i)}, \mathbf{d}), \quad (35)$$

where $\boldsymbol{\theta}_{\mathcal{M}}^{(i)} \sim p(\boldsymbol{\theta}_{\mathcal{M}}|\mathcal{M}, \mathbf{d})$. If one assumes the models can fully represent the experiments, then $\sum_{\mathcal{M}} p(\mathcal{M}) = 1$. The posterior probability of the model \mathcal{M} can then be normalized as $p(\mathcal{M}|\mathbf{Y}^{\text{D}}, \mathbf{d}) / \sum_{\mathcal{M}} p(\mathcal{M}|\mathbf{Y}^{\text{D}}, \mathbf{d})$. The obtained posterior distribution,

$$p(\boldsymbol{\theta}|\mathbf{Y}_{1:N_{\text{Des}}}, \mathbf{d}_{1:N_{\text{Des}}}) = p(\mathcal{M}|\mathbf{Y}_{1:N_{\text{Des}}}, \mathbf{d}_{1:N_{\text{Des}}}) p(\boldsymbol{\theta}_{\mathcal{M}}|\mathcal{M}, \mathbf{Y}_{1:N_{\text{Des}}}, \mathbf{d}_{1:N_{\text{Des}}}), \quad (36)$$

is subsequently used to update the prior for [algorithm 1](#) to obtain the next optimal design point.

An algorithm for IMR-based model inference is presented in [algorithm 2](#). Together with [algorithm 1](#), these form a complete loop for the simulation-based characterization of soft matter, as illustrated in [fig. 1](#).

5 Results

We demonstrate the proposed framework using two numerical datasets generated using the IMR method. The underlying models for these two datasets are chosen to mimic the viscoelastic

Algorithm 2 Model inference (refer to [fig. 1\(c\)](#) for graphical illustration)

Input: target design \mathbf{d} , prior distribution $p(\boldsymbol{\theta}|\mathbf{d}_{1:N_{\text{Des}}})$
Output: posterior distribution $p((\boldsymbol{\theta}_{\mathcal{M}}, \mathcal{M})|\mathbf{Y}^{\text{D}}, \mathbf{d})$

- 1: Collect data \mathbf{Y}^{D} at the design \mathbf{d} with error $\boldsymbol{\Sigma}$
- 2: **for** each model \mathcal{M} **do**
- 3: **for** $l = 1 : N_r$ **do**
- 4: Draw N_{En} samples $(\tilde{\boldsymbol{\theta}}_0^{(1)}, \dots, \tilde{\boldsymbol{\theta}}_0^{(N_{\text{En}})})$ from the prior distribution $p(\boldsymbol{\theta}_{\mathcal{M}}|\mathcal{M}, \mathbf{d}_{1:N_{\text{Des}}})$
- 5: Generate N_{En} initial ensembles $\tilde{\mathbf{Q}}_0 = (\tilde{\mathbf{Q}}_0^{(1)}, \dots, \tilde{\mathbf{Q}}_0^{(N_{\text{En}})})$
- 6: Perform En4D-Var with N_{iter} iterations to update the ensembles $\tilde{\mathbf{Q}}_0$
- 7: Perform covariance inflation and update the prior distribution
- 8: **end for**
- 9: Calculate the marginal likelihood $p(\mathcal{M}|\mathbf{Y}^{\text{D}}, \mathbf{d})$ using [\(35\)](#)
- 10: **end for**
- 11: Normalize the model probability to obtain the posterior distribution $p((\boldsymbol{\theta}_{\mathcal{M}}, \mathcal{M})|\mathbf{Y}^{\text{D}}, \mathbf{d})$
- 12: Update the prior $p(\boldsymbol{\theta}|\mathbf{d}_{1:N_{\text{Des}}+1})$ for [algorithm 1](#) to obtain the next design point

Table 3: Summary of synthetic datasets. The characterization of these parameters from experimental data is demonstrated in Yang et al. [\[11\]](#).

	Material	Model \mathcal{M}	Parameters $\boldsymbol{\theta}_{\mathcal{M}}$			
			G_{∞} [kPa]	G [kPa]	μ [Pa.s]	α
Case 1	Stiff PA	qKV	2.77	—	0.186	0.48
Case 2	Soft PA	NHKV	0.57	8.31	0.093	—

behavior of stiff and soft PA hydrogels [\[11\]](#). The details are summarized in [table 3](#). To align these simulation-based datasets with real-world experimental measurements, we introduce synthetic error to accommodate various sources of error. These include uncertainties in measurement errors and aliasing in the bubble response. The standard deviations of this synthetic noise, $\sigma = |R^* - 1|/50 + t^*/160$, are tailored to depend on time and state, reflecting experimental measurements. A longer duration of measurement or being closer to bubble collapse will result in a larger error, as illustrated in [fig. 4](#). A set of measurements containing 100 $R(t)$ curves is collected for each design. We aim to accurately characterize the underlying model with a minimum requirement of design iterations using the optimal sequential design process, as shown in [fig. 1](#). We consider two candidate models, NHKV and Gen. qKV, to demonstrate the proposed framework at a reasonable computational cost. The design is initialized with a probability of 50%–50% for these two models. To better represent real-world experiments, the optimization problems for the design parameters are restricted within the ranges $We \in [100, 1000]$ and $R_{\infty}^* \in [0.14, 0.3]$, respectively. In the computation, the data assimilation window is set up to the first two peaks of the bubble collapse. For each set of measurements, En4D-Var is run $N_{\text{runs}} = 3$ times (with 2 restarts), using 5 iterations for each run and an ensemble size of $N_{\text{En}} = 48$. This choice of ensemble size follows Spratt et al. [\[55\]](#). Later, we will show that the above setup is enough to characterize the underlying model of synthetic data. Quantitative assessment metrics include EIG, root-mean-square error (RMSE) of the $R(t)$ curves and the relative error of the material properties.

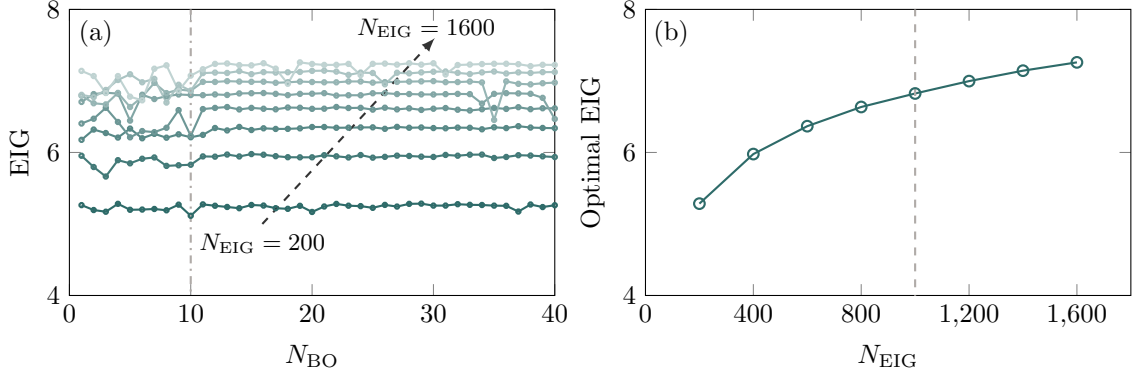


Figure 2: BO output trajectories (a) and the optimal BO outputs (b) for EIG sample sizes $N_{\text{EIG}} = 200, 400, \dots, 1600$. The dot-dashed line in (a) indicates the onset of the BO process with 10 initial trials. The optimal EIG for the EIG sample size used later, $N_{\text{EIG}} = 1000$, is highlighted in (b).

5.1 qKV for stiff PA

We first consider qKV as the underlying model to approximate the behavior of stiff PA [11]. We assume that the quasistatic shear modulus can be measured with $G_{\infty} = (2.77 \pm 0.30)$ kPa, which has a much higher variance compared to the actual experimental measurements. The prior distributions of the material properties are set as $G = (15.09 \pm 4.35)$ kPa, $\mu = (0.209 \pm 0.180)$ Pa s for NHKV and $\mu = (0.286 \pm 0.186)$ Pa s, $\alpha = 0.28 \pm 0.48$ for Gen. qKV, respectively. The latter has around 50% error compared to the underlying truth, which has been shown as a reasonable offset to validate the performance of DA [55]. Truncated Gaussian distributions [78] ensures $\mu > 0$ such that the material properties are physically interpretable.

We first show the results of the simulation-based BOED in section 3 using the aforementioned prior distributions as an example. Figure 2 (a) shows the BO outputs for different sample sizes used to estimate the EIG. In general, the observed EIG increases as the sample size grows. With an initialization of 10 random trials, only a few more trials are necessary to reach the optimal EIG values. These values are shown in fig. 2 (b) for different sample sizes, and a convergence trend can be observed. Based on these observations, we will estimate the EIG using a sample size of $N_{\text{EIG}} = 1000$ and perform $N_{\text{BO}} = 15$ trials for BO in the design process to achieve a reasonable balance between accuracy and computational efficiency.

Next, we collect measurements at the optimal design and perform data assimilation to obtain the posterior distributions. For example, fig. 3 shows the DA outputs using the initial prior distributions for Gen. qKV. As expected, the variance of the ensembles decreases with more DA iterations. Despite an initial guess of approximately 50% error, using En4D-Var enables accurate identification of the true material properties. It can be observed that the restart strategy with covariance inflation enhances the posterior distributions with more restart runs, leading to a decrease in the RMSE of the ensemble $R(t)$ curves. Compared to the standard En4D-Var in Spratt et al. [55], drawing fresh samples when restarting helps avoid local minima due to initial bias in ensembles.

The final step of the sequential design is to calibrate the model probabilities based on the measurements and posteriors. Figure 4 shows the RMSE and the model probabilities by comparing the posterior $R(t)$ curves to the measurements for two designs. For each design, both models show favorable bubble dynamics compared to the average of measurements, resulting in similar RMSE. On the other hand, the likelihoods of these two models offer a different perspective for model selection by considering the variance present in the data. For the design shown in fig. 4 (a, c), NHKV and

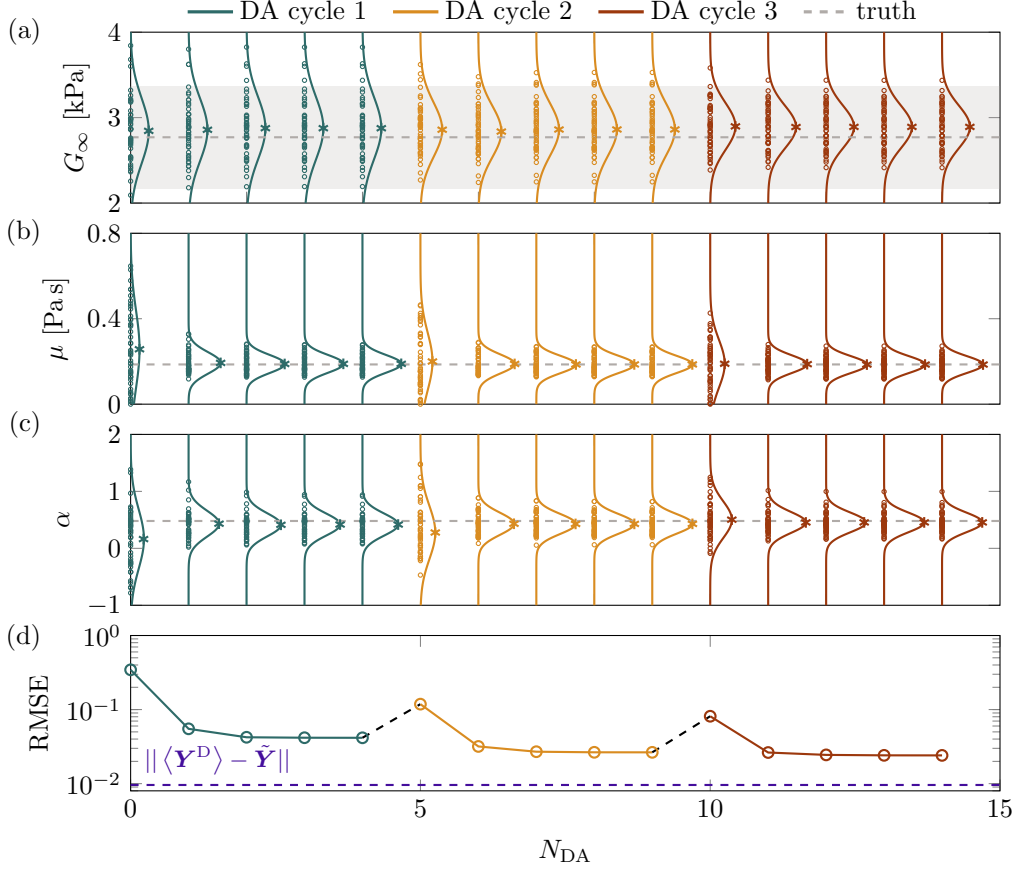


Figure 3: DA outputs over the total En4D-var iteration number N_{DA} : ensembles for (a) G_∞ ; (b) μ ; (c) α ; and (d) RMSE of the bubble dynamics curves. The shaded area in (a) represents the 95% confidence interval for the G_∞ measurements. The solid curves in (a–c) represent Gaussian distributions approximated from the 48 ensembles, with their respective mean values marked as stars. In (d), the error between the mean of the measurements and the unobtainable truth, $\|\langle \mathbf{Y}^D \rangle - \tilde{\mathbf{Y}}\|$, is shown for comparison.

Gen. qKV show comparable model probability. Conversely, for the other case in fig. 4 (b, d), the preference for Gen. qKV over NHKV is unequivocal. These findings are also visually corroborated. These model probabilities are subsequently used to update the prior distribution to estimate the optimal EIG for the next design point. The processes shown in figs. 2 to 4 are repeated.

Figure 5 shows the results for the sequential BOED. As the number of measurements increases, there is a general trend of increased exploration of parameter space and higher model probability for Gen. qKV, leading to a decrease in the EIG. Conversely, the total EIG continues to rise due to inherent measurement uncertainties. Accurate identification of the material properties for Gen. qKV can be seen from fig. 5 (c) in terms of the relative error. The mean material properties converge across approximately 10 designs, coinciding with a reduction in their variances to levels deemed negligible (not shown). The convergence of G_∞ to the ground truth suggests that the Gen. qKV model effectively reduces to the standard qKV model with a constant quasistatic shear modulus. These findings indicate that the sequential approach effectively characterizes the underlying qKV model despite various error sources. Compared to the random design, the optimal sequential BOED demonstrates superior EIG, model probability, and relative error performance, showing that the proposed approach can accurately and efficiently characterize the underlying soft material from

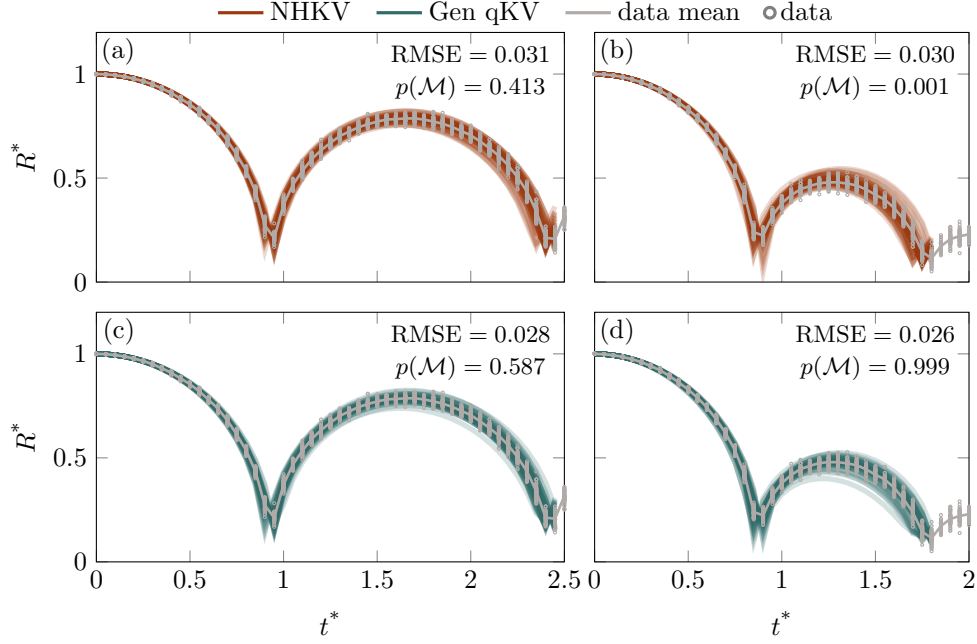


Figure 4: Posterior bubble dynamics trajectories and their marginal likelihoods: (a, c) $R_{\max} = 9.85 \times 10^{-4}$ m and $R_{\infty}^* = 0.2887$; (b, d) $R_{\max} = 3.87 \times 10^{-4}$ m and $R_{\infty}^* = 0.15$.

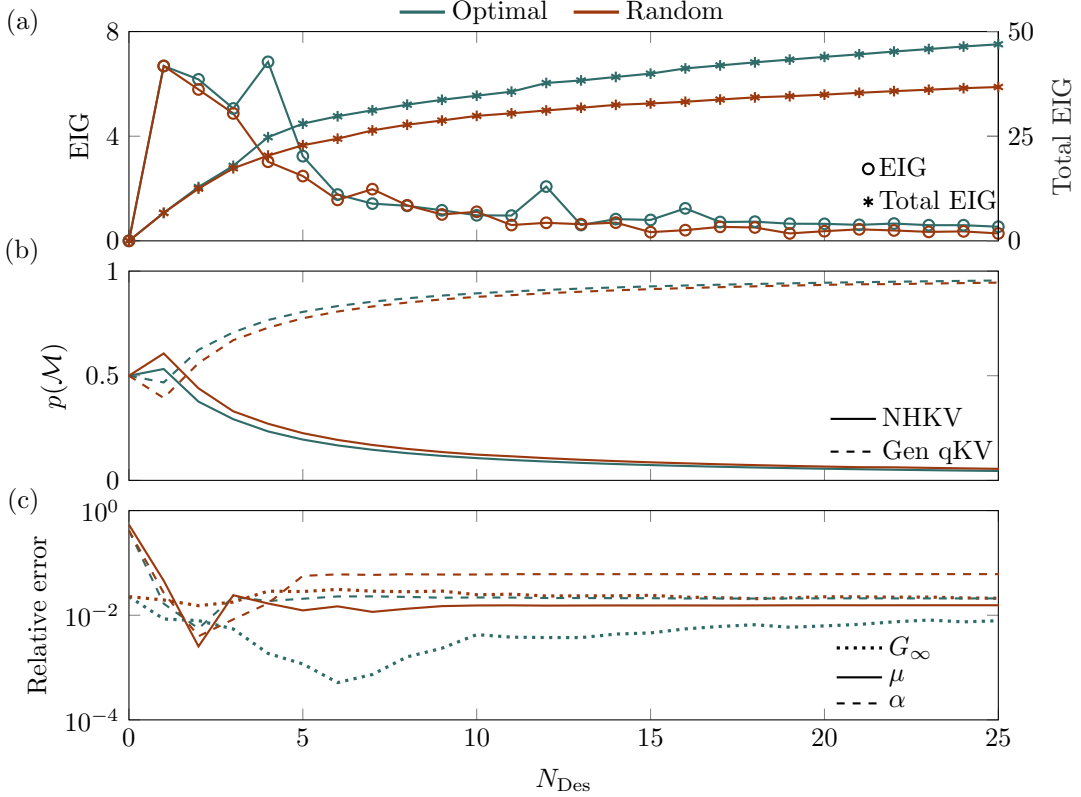


Figure 5: Sequential BOED outputs over the design number N_{Des} : (a) EIG and total EIG; (b) model probabilities; and (c) relative error of the mean material properties.

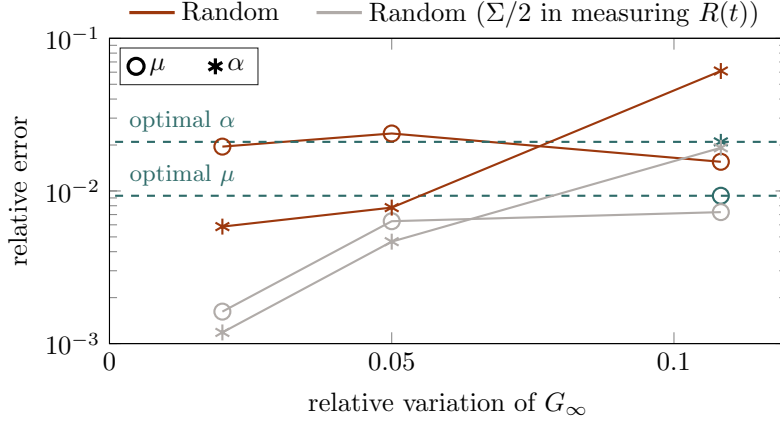


Figure 6: Convergence study of different error sources.

bubble dynamics.

Finally, we examine the effects of different error sources within the system, as shown in fig. 6. The accuracy of the stiff-straining parameter, α , improves as the variation of the quasistatic shear modulus, G_∞ , decreases to the real experimental error of 2%, see, e.g., Estrada et al. [1]. This relationship aligns with the fact that these two parameters collectively represent a material’s resistance to shearing deformation under shearing stress, see (2). A more accurate determination of the viscosity, μ , requires smaller measurement errors in the bubble radius, R . This correspondence can also be inferred from (2) due to the coupled contributions of μ and R to the stress integral. For example, the optimal design is conducted considering high measurement noise in both R and G_∞ , and the outputs demonstrate significant improvement compared to the random design. By reducing the error in both sources, we anticipate accurately identifying the two parameters with a relative error of approximately 0.1%, as is the case for the random design.

5.2 NHKV for soft PA

Next, we consider NHKV as the underlying model to approximate the behavior of soft PA [11]. Consistent with the previous case, we initialize the prior distributions of the NHKV material properties as $G = (12.00 \pm 6.35)$ kPa and $\mu = (0.140 \pm 0.073)$ Pa s to allow for approximately a 50% error compared to the actual truth. For Gen. qKV, we assume that the quasistatic shear modulus is measured with $G_\infty = (0.57 \pm 0.06)$ kPa and the prior distributions are set as $\mu = (0.08 \pm 0.05)$ Pa s, $\alpha = 0.96 \pm 0.48$.

We repeat the process shown in section 5.1 and show the sequential BOED results for the synthetic soft PA in fig. 7. The overall trend is qualitatively similar to those presented in fig. 5. These 12 designs accurately characterize the underlying NHKV model and its material properties. Although the optimal designs are chosen by maximizing information gains instead of minimizing errors in material properties, they yield significantly improved results for μ and comparable outcomes for G relative to the random design. Collectively, sections 5.1 and 5.2 illustrate that the proposed method can accurately and efficiently characterize the mechanical behaviors of various soft materials.

6 Limitations of present work

The application of En4D-Var for data assimilation achieves computational efficiency by assuming that material properties, such as shear modulus and viscosities, follow a multivariate normal distribution.

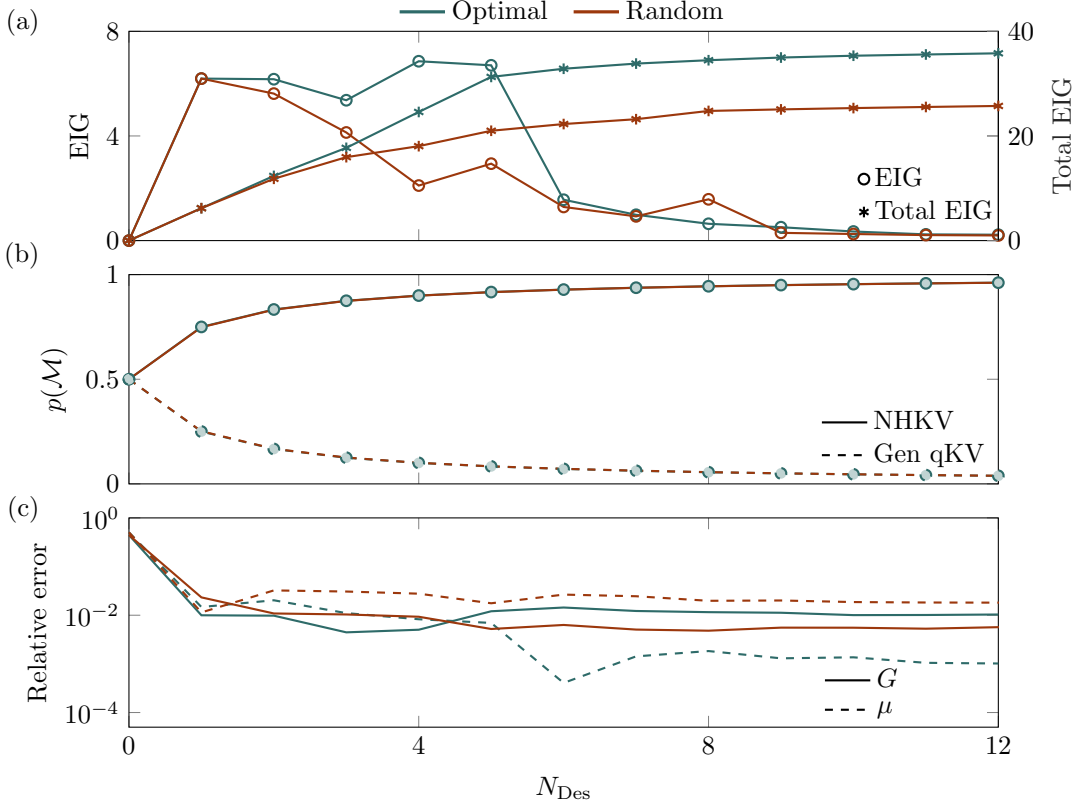


Figure 7: Sequential BOED outputs over the design number N_{Des} : (a) EIG and total EIG; (b) model probabilities $p(\mathcal{M})$; and (c) relative error of the mean material properties.

Consequently, its performance will deteriorate when the soft materials under characterization do not adhere to this assumption. Other Bayesian parameter inference methods, such as Markov chain Monte Carlo (MCMC) sampling, can address this issue but often require many samples to compute posterior estimates with acceptable accuracy. As suggested by Kruschke [79], a minimum sample size for an effective MCMC process is 10^4 , significantly higher than the En4D-Var ensemble size used in this work, $N_{\text{En}} = 48$. Therefore, balancing the number of measurements required for posterior sampling and the constraints imposed on the distributions of the material properties becomes necessary for analyzing real experimental data. Conducting a prior assessment of the test samples could potentially aid in achieving this balance.

The proposed approach necessitates knowledge of the underlying theoretical models as a *prior* for optimal design and parameter inference. Specifically, in our context, this information includes the constitutive models used within the spherical bubble dynamics equations. While the modal probability calculation yields the marginal likelihoods for each constitutive model under consideration, it does not provide further insights beyond these models. If all the available models inadequately represent the experimental measurements, data-driven modeling approaches, such as system identification or operator inference methods, offer a viable strategy for exploring alternative models.

7 Conclusions

This study presents a computational approach for the optimal design of experiments to accelerate the discovery of material properties. To generate synthetic data that aligns with real experiments,

we used inertial microcavitation rheometry (IMR) for accurate and efficient bubble dynamics simulations. By incorporating appropriate noise to account for model error and measurement noises, these simulations serve as predictions of bubble dynamics trajectories under specific experimental conditions during the optimal design phase and as synthetic measurements during the parameter inference phase. We formulated the optimization problem within a Bayesian statistical framework to design experiments that provide the most informative data about unknown material properties. The constitutive models and associated viscoelastic properties are then determined from the measurements using a hybrid ensemble-based 4D-Var method (En4D-Var). By iterating these two processes sequentially, we demonstrated accurate and efficient characterizations of two types of synthetic polyacrylamide (PA) gels. The robustness of the IMR-based design approach is evidenced by the larger error in each source of synthetic data compared to real experimental measurements, underscoring its potential applicability to actual experimental designs.

CRedit authorship contribution statement

TC: Formal analysis, Methodology, Software, Investigation, Data Curation, Validation, Visualization, Writing – original draft. **JBE:** Conceptualization, Funding acquisition, Methodology, Project administration, Resources, Writing – review & editing. **SHB:** Conceptualization, Funding acquisition, Methodology, Project administration, Resources, Supervision, Writing – review & editing.

Declaration of competing interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Acknowledgments

The authors acknowledge support from the U.S. Department of Defense, the Army Research Office under Grant No. W911NF-23-10324 (PMs Drs. Denise Ford and Robert Martin). This work used PSC Bridges2 and NCSA Delta through allocation PHY210084 (PI Bryngelson) from the Advanced Cyberinfrastructure Coordination Ecosystem: Services & Support (ACCESS) program [80], which is supported by National Science Foundation grants #2138259, #2138286, #2138307, #2137603, and #2138296.

References

- [1] J. B. Estrada, C. Barajas, D. L. Henann, E. Johnsen, C. Franck, High strain-rate soft material characterization via inertial cavitation, *J. Mech. Phys. Solids* **112** (2018) 291–317.
- [2] L. Mancia, E. Vlaisavljevich, N. Yousefi, M. Rodriguez, T. J. Ziemlewicz, F. T. Lee, D. Henann, C. Franck, Z. Xu, E. Johnsen, Modeling tissue-selective cavitation damage, *Phys. Med. Biol.* **64** (2019) 225001.
- [3] E. Vlaisavljevich, A. Maxwell, L. Mancia, E. Johnsen, C. Cain, Z. Xu, Visualizing the histotripsy process: Bubble cloud–cancer cell interactions in a tissue-mimicking environment, *Ultrasound Med. Biol.* **42** (2016) 2466–2477.
- [4] E.-A. Brujan, A. Vogel, Stress wave emission and cavitation bubble dynamics by nanosecond optical breakdown in a tissue phantom, *J. Fluid Mech.* **558** (2006) 281–308.

- [5] M. R. Bailey, V. A. Khokhlova, O. A. Sapozhnikov, S. G. Kargl, L. A. Crum, Physical mechanisms of the therapeutic effect of ultrasound (a review), *Acoust. Phys.* **49** (2003) 369–388.
- [6] C. E. Brennen, Cavitation in medicine, *Interface Focus* **5** (2015) 20150022.
- [7] P. D. Arora, N. Narani, C. A. G. McCulloch, The compliance of collagen gels regulates transforming growth factor- β induction of α -smooth muscle actin in fibroblasts, *Am. J. Pathol.* **154** (1999) 871–882.
- [8] W. W. Chen, B. Song, *Split Hopkinson (Kolsky) Bar: Design, Testing and Applications*, Springer Science & Business Media, 2010.
- [9] D. C. Lin, D. I. Shreiber, E. K. Dimitriadis, F. Horkay, Spherical indentation of soft matter beyond the hertzian regime: numerical and experimental validation of hyperelastic models, *Biomech. Model Mechanobiol.* **8** (2009) 345–358.
- [10] R. W. Style, C. Hyland, R. Boltyanskiy, J. S. Wettlaufer, E. R. Dufresne, Surface tension and contact with soft elastic solids, *Nat. Commun.* **4** (2013) 2728.
- [11] J. Yang, H. C. Cramer III, C. Franck, Extracting non-linear viscoelastic material properties from violently-collapsing cavitation bubbles, *Extreme Mech. Lett.* **39** (2020) 100839.
- [12] S. Buyukozturk, J.-S. Spratt, D. L. Henann, T. Colonius, C. Franck, Particle-assisted laser-induced inertial cavitation for high strain-rate soft material characterization, *Exp. Mech.* **62** (2022) 1037–1050.
- [13] L. Mancía, J. Yang, J.-S. Spratt, J. R. Sukovich, Z. Xu, T. Colonius, C. Franck, E. Johnsen, Acoustic cavitation rheometry, *Soft Matter* **17** (2021) 2931–2941.
- [14] J. Yang, H. C. Cramer III, E. C. Bremer, S. Buyukozturk, Y. Yin, C. Franck, Mechanical characterization of agarose hydrogels and their inherent dynamic instabilities at ballistic to ultra-high strain-rates via inertial microcavitation, *Extreme Mech. Lett.* **51** (2022) 101572.
- [15] E. C. Bremer-Sai, J. Yang, A. McGhee, C. Franck, Ballistic and blast-relevant, high-rate material properties of physically and chemically crosslinked hydrogels, *Exp. Mech.* **64** (2024) 587–592.
- [16] C. López-Fagundo, E. Bar-Kochba, L. L. Livi, D. Hoffman-Kim, C. Franck, Three-dimensional traction forces of Schwann cells on compliant substrates, *J. R. Soc. Interface* **11** (2014) 20140247.
- [17] D. V. Lindley, On a measure of the information provided by an experiment, *Ann. Math. Stat.* **27** (1956) 986–1005.
- [18] J. Lewi, R. Butera, L. Paninski, Sequential optimal design of neurophysiology experiments, *Neural Comput.* **21** (2009) 619–687.
- [19] D. R. Cavagnaro, J. I. Myung, M. A. Pitt, J. V. Kujala, Adaptive design optimization: A mutual information-based approach to model discrimination in cognitive science, *Neural Comput.* **22** (2010) 887–905.
- [20] Q. Long, M. Scavino, R. Tempone, S. Wang, Fast estimation of expected information gains for Bayesian experimental designs based on laplace approximations, *Comput. Methods Appl. Mech. Eng.* **259** (2013) 24–39.

- [21] E. G. Ryan, C. C. Drovandi, M. H. Thompson, A. N. Pettitt, Towards Bayesian experimental design for nonlinear models that require a large number of sampling times, *Comput. Stat. Data Anal.* **70** (2014) 45–60.
- [22] M. Hamada, H. F. Martz, C. S. Reese, A. G. Wilson, Finding near-optimal Bayesian experimental designs via genetic algorithms, *Am. Stat.* **55** (2001) 175–181.
- [23] K. J. Ryan, Estimating expected information gains for experimental designs with application to the random fatigue-limit model, *J. Comput. Graph.* **12** (2003) 585–603.
- [24] X. Huan, Y. M. Marzouk, Simulation-based optimal Bayesian experimental design for nonlinear systems, *J. Comput. Phys.* **232** (2013) 288–317.
- [25] J. I. Myung, D. R. Cavagnaro, M. A. Pitt, A tutorial on adaptive design optimization, *J. Math. Psychol.* **57** (2013) 53–67.
- [26] A. Foster, M. Jankowiak, E. Bingham, P. Horsfall, Y. W. Teh, T. Rainforth, N. Goodman, Variational Bayesian optimal experimental design, *Adv. Neural Inf. Process Syst.* **32** (2019).
- [27] A. Foster, M. Jankowiak, M. O’Meara, Y. W. Teh, T. Rainforth, A unified stochastic gradient approach to designing Bayesian-optimal experiments, in: *AISTATS, 2020*, pp. 2959–2969.
- [28] E. G. Ryan, C. C. Drovandi, J. M. McGree, A. N. Pettitt, A review of modern computational algorithms for Bayesian optimal design, *Int. Stat. Rev.* **84** (2016) 128–154.
- [29] T. Rainforth, A. Foster, D. R. Ivanova, F. Bickford Smith, Modern Bayesian experimental design, *Stat. Sci.* **39** (2024) 100–114.
- [30] P. Müller, Simulation-based optimal design, *Handbook Stat.* **25** (2005) 509–518.
- [31] B. Amzal, F. Y. Bois, E. Parent, C. P. Robert, Bayesian-optimal design via interacting particle systems, *J. Am. Stat. Assoc.* **101** (2006) 773–785.
- [32] X. Huan, Y. M. Marzouk, Gradient-based stochastic optimization methods in Bayesian experimental design, *Int. J. Uncertain. Quan.* **4** (2014).
- [33] A. G. Carlon, B. M. Dia, L. Espath, R. H. Lopez, R. Tempone, Nesterov-aided stochastic gradient methods using Laplace approximation for Bayesian design optimization, *Comput. Methods Appl. Mech. Eng.* **363** (2020) 112909.
- [34] A. Karimi, L. Taghizadeh, C. Heitzinger, Optimal Bayesian experimental design for electrical impedance tomography in medical imaging, *Comput. Methods Appl. Mech. Eng.* **373** (2021) 113489.
- [35] S. Kleinegesse, M. U. Gutmann, Bayesian experimental design for implicit models by mutual information neural estimation, in: *ICML, 2020*, pp. 5316–5326.
- [36] F. Häse, M. Aldeghi, R. J. Hickman, L. M. Roch, A. Aspuru-Guzik, Gryffin: An algorithm for Bayesian optimization of categorical variables informed by expert knowledge, *Appl. Phys. Rev.* **8** (2021).
- [37] B. Shahriari, K. Swersky, Z. Wang, R. P. Adams, N. De Freitas, Taking the human out of the loop: A review of Bayesian optimization, *Proc. IEEE* **104** (2015) 148–175.

- [38] J. Snoek, H. Larochelle, R. P. Adams, Practical Bayesian optimization of machine learning algorithms, *Adv. Neural Inf. Process. Syst.* **25** (2012).
- [39] P. Müller, D. A. Berry, A. P. Grieve, M. Smith, M. Krams, Simulation-based sequential Bayesian design, *J. Stat. Plan. Infer.* **137** (2007) 3140–3150.
- [40] W. Kim, M. A. Pitt, Z.-L. Lu, M. Steyvers, J. I. Myung, A hierarchical adaptive approach to optimal experimental design, *Neural Comput.* **26** (2014) 2465–2492.
- [41] X. Huan, Y. M. Marzouk, Sequential Bayesian optimal experimental design via approximate dynamic programming, *arXiv preprint arXiv:1604.08320* (2016).
- [42] G. Evensen, Sequential data assimilation with a nonlinear quasi-geostrophic model using Monte Carlo methods to forecast error statistics, *J. Geophys. Res. Oceans* **99** (1994) 10143–10162.
- [43] G. Evensen, The ensemble Kalman filter: Theoretical formulation and practical implementation, *Ocean Dyn.* **53** (2003) 343–367.
- [44] P. Sakov, F. Counillon, L. Bertino, K. A. Lisæter, P. R. Oke, A. Korablev, Topaz4: An ocean-sea ice data assimilation system for the North Atlantic and Arctic, *Ocean Sci.* **8** (2012) 633–656.
- [45] P. L. Houtekamer, H. L. Mitchell, Data assimilation using an ensemble Kalman filter technique, *Mon. Weather Rev.* **126** (1998) 796–811.
- [46] G. Burgers, P. J. Van Leeuwen, G. Evensen, Analysis scheme in the ensemble Kalman filter, *Mon. Weather Rev.* **126** (1998) 1719–1724.
- [47] J. S. Whitaker, T. M. Hamill, Ensemble data assimilation without perturbed observations, *Mon. Weather Rev.* **130** (2002) 1913–1924.
- [48] S. I. Aanonsen, G. Nøvdal, D. S. Oliver, A. C. Reynolds, B. Vallès, The ensemble Kalman filter in reservoir engineering—a review, *SPE J.* **14** (2009) 393–412.
- [49] G. Evensen, P. J. Van Leeuwen, An ensemble Kalman smoother for nonlinear dynamics, *Mon. Weather Rev.* **128** (2000) 1852–1867.
- [50] M. Bocquet, P. Sakov, An iterative ensemble Kalman smoother, *Q. J. R. Meteorol. Soc.* **140** (2013) 1521–1535.
- [51] P. Sakov, D. S. Oliver, L. Bertino, An iterative EnKF for strongly nonlinear systems, *Mon. Weather Rev.* **140** (2012) 1988–2004.
- [52] C. Liu, Q. Xiao, B. Wang, An ensemble-based four-dimensional variational data assimilation scheme. part i: Technical formulation and preliminary test, *Mon. Weather Rev.* **136** (2008) 3363–3373.
- [53] N. Gustafsson, J. Bojarova, Four-dimensional ensemble variational (4D-En-Var) data assimilation for the high-resolution limited area model (HIRLAM), *Nonlinear Proc. Geoph.* **21** (2014) 745–762.
- [54] A. Carrassi, M. Bocquet, L. Bertino, G. Evensen, Data assimilation in the geosciences: An overview of methods, issues, and perspectives, *Wiley Interdiscip. Rev. Clim.* **9** (2018) e535.

- [55] J.-S. Spratt, M. Rodriguez, K. Schmidmayer, S. H. Bryngelson, J. Yang, C. Franck, T. Colonius, Characterizing viscoelastic materials via ensemble-based data assimilation of bubble collapse observations, *J. Mech. Phys. Solids* **152** (2021) 104455.
- [56] L. Wasserman, Bayesian model selection and model averaging, *J. Math. Psychol.* **44** (2000) 92–107.
- [57] H. Chipman, E. I. George, R. E. McCulloch, M. Clyde, D. P. Foster, R. A. Stine, The practical implementation of Bayesian model selection, *Lect. Notes-Monogr. Ser.* (2001) 65–134.
- [58] R. Gaudron, M. T. Warnez, E. Johnsen, Bubble dynamics in a viscoelastic medium with nonlinear elasticity, *J. Fluid Mech.* **766** (2015) 54–75.
- [59] X. Yang, C. C. Church, A model for the dynamics of gas bubbles in soft tissue, *J. Acoust. Soc. Am.* **118** (2005) 3595–3606.
- [60] C. T. Wilson, T. L. Hall, E. Johnsen, L. Mancia, M. Rodriguez, J. E. Lundt, T. Colonius, D. L. Henann, C. Franck, Z. Xu, et al., Comparative study of the dynamics of laser and acoustically generated bubbles in viscoelastic media, *Phys. Rev. E* **99** (2019) 043103.
- [61] C. Barajas, E. Johnsen, The effects of heat and mass diffusion on freely oscillating bubbles in a viscoelastic, tissue-like medium, *J. Acoust. Soc. Am.* **141** (2017) 908–918.
- [62] J. B. Keller, M. Miksis, Bubble oscillations of large amplitude, *J. Acoust. Soc. Am.* **68** (1980) 628–633.
- [63] I. Akhatov, O. Lindau, A. Topolnikov, R. Mettin, N. Vakhitova, W. Lauterborn, Collapse and rebound of a laser-induced cavitation bubble, *Phys. Fluids* **13** (2001) 2805–2819.
- [64] R. I. Nigmatulin, N. S. Khabeev, F. B. Nagiev, Dynamics, heat and mass transfer of vapour-gas bubbles in a liquid, *Int. J. Heat Mass Transf.* **24** (1981) 1033–1044.
- [65] Y.-C. Fung, *Biomechanics: Mechanical Properties of Living Tissues*, Springer Science & Business Media, 2013.
- [66] J. K. Knowles, The finite anti-plane shear field near the tip of a crack for a class of incompressible elastic solids, *Int. J. Fract.* **13** (1977) 611–639.
- [67] J. Toyjanova, E. Hannen, E. Bar-Kochba, E. M. Darling, D. L. Henann, C. Franck, 3d viscoelastic traction force microscopy, *Soft Matter* **10** (2014) 8095–8106.
- [68] J.-S. Spratt, *Numerical Simulations of Cavitating Bubbles in Elastic and Viscoelastic Materials for Biomedical Applications*, California Institute of Technology, 2024.
- [69] J. B. Freund, R. H. Ewoldt, Quantitative rheological model selection: Good fits versus credible models using Bayesian inference, *J. Rheol.* **59** (2015) 667–701.
- [70] D. R. Jones, M. Schonlau, W. J. Welch, Efficient global optimization of expensive black-box functions, *J. Global Optim.* **13** (1998) 455–492.
- [71] K. Kandasamy, K. R. Vysyaraju, W. Neiswanger, B. Paria, C. R. Collins, J. Schneider, B. Poczos, E. P. Xing, Tuning hyperparameters without grad students: Scalable and robust Bayesian optimisation with dragonfly, *J. Mach. Learn. Res.* **21** (2020) 1–27.

- [72] L. Benjamin, K. Brian, O. Guilherme, B. Eytan, Constrained Bayesian optimization with noisy experiments, *Bayesian Anal.* **14** (2019) 495 – 519.
- [73] D. Eriksson, M. Poloczek, Scalable constrained Bayesian optimization, in: *AISTATS*, 2021, pp. 730–738.
- [74] M. Zafari, A. C. Reynolds, Assessing the uncertainty in reservoir description and performance predictions with the ensemble Kalman filter, in: *SPE J.*, 2005, pp. SPE–95750.
- [75] Y. Gu, D. S. Oliver, An iterative ensemble Kalman filter for multiphase fluid flow data assimilation, *SPE J.* **12** (2007) 438–446.
- [76] H.-J. Hendricks Franssen, W. Kinzelbach, Real-time groundwater flow modeling with the ensemble Kalman filter: Joint estimation of states and parameters and the filter inbreeding problem, *Water Resour. Res.* **44** (2008).
- [77] J. S. Whitaker, T. M. Hamill, Evaluating methods to account for system errors in ensemble data assimilation, *Mon. Weather Rev.* **140** (2012) 3078–3089.
- [78] C. P. Robert, Simulation of truncated normal variables, *Stat. Comput.* **5** (1995) 121–125.
- [79] J. Kruschke, *Doing Bayesian Data Analysis*, Academic Press, 2014.
- [80] T. J. Boerner, S. Deems, T. R. Furlani, S. L. Knuth, J. Towns, Access: Advancing innovation: NSF’s advanced cyberinfrastructure coordination ecosystem: Services & support, in: *PEARC*, 2023, pp. 173–176.